


NEW YORK STATE
DEPARTMENT OF TRANSPORTATION
MATERIALS BUREAU
JOB MIX FORMULA

Facility No. H0395 Formula No. _____
Plant City Asphalt Region 11
Plant Location Staten Island, NY
Submitted By Maxon Thomas Date 4/7/2020

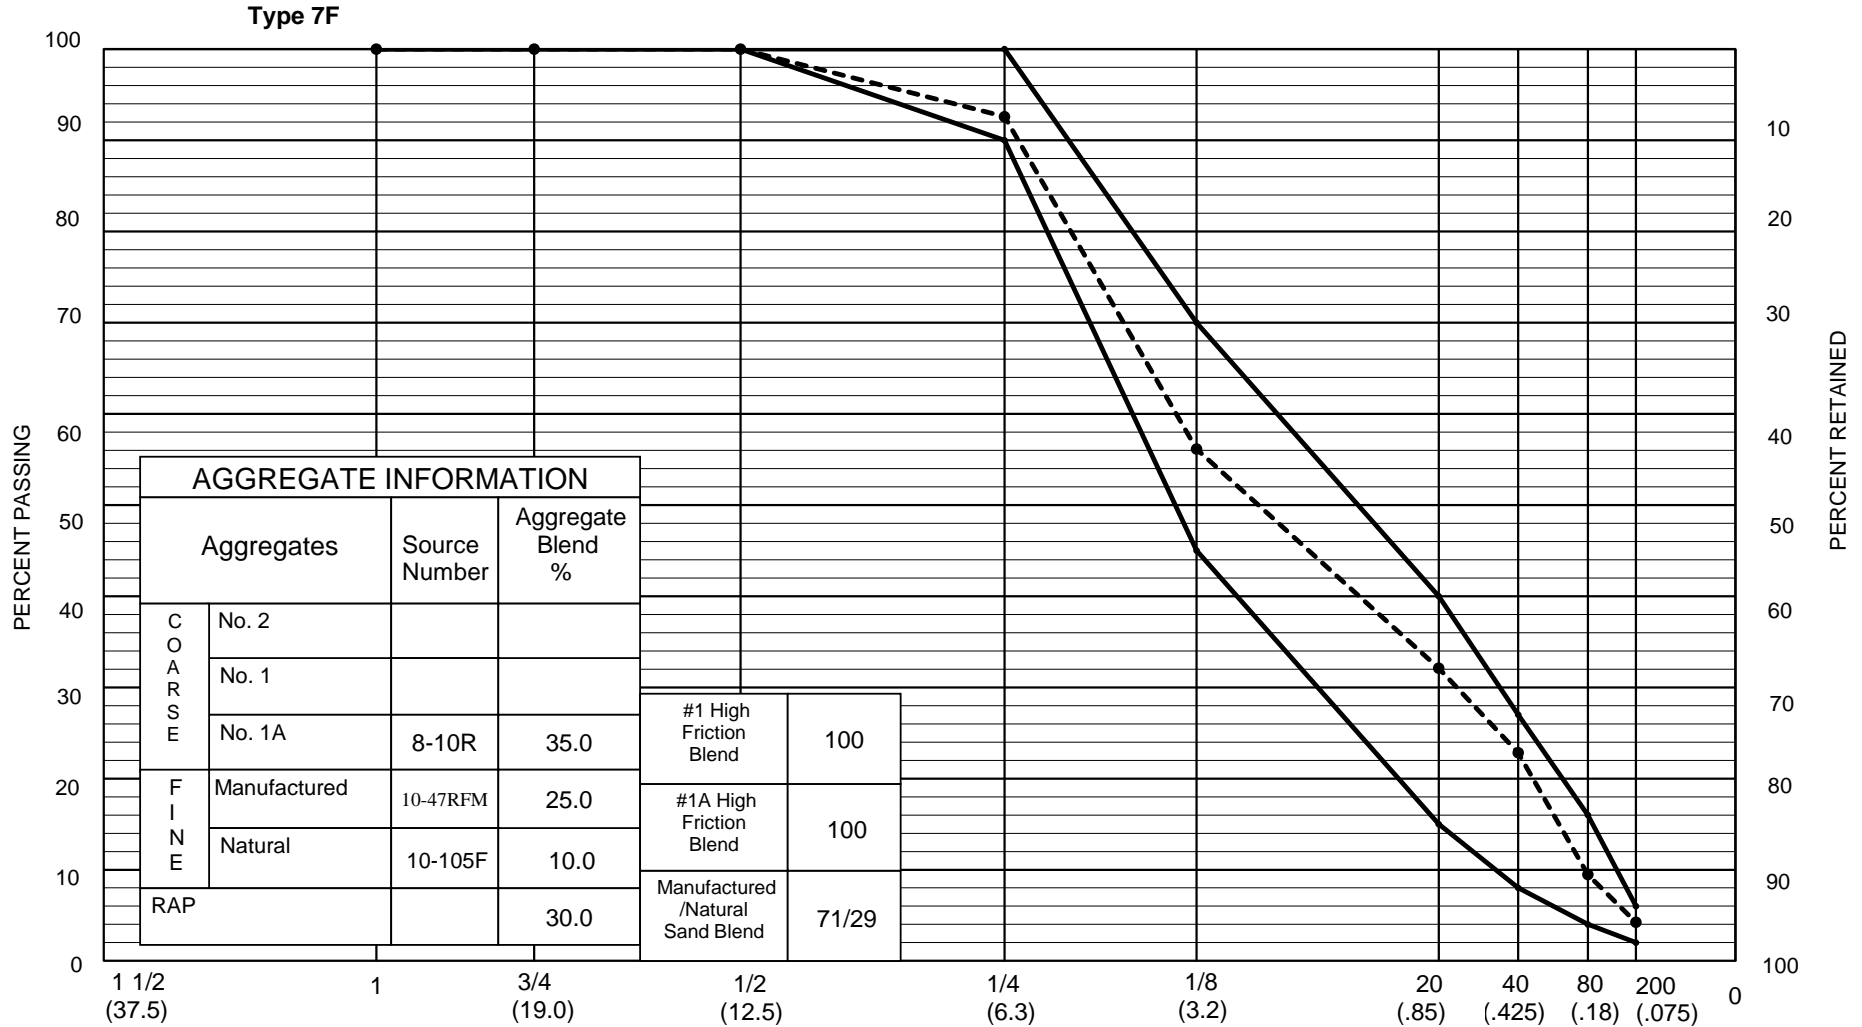

U.S. STD. - SIZES RAISED TO 0.45 POWER

Sieve Size	1 1/2" (37.5)	1" (25.0)	3/4" (19.0)	1/2" (12.5)	1/4" (6.3)	1/8" (3.2)	20 (0.850)	40 (0.425)	80 (0.180)	200(0.075)	Asphalt Content (Percent)	
% Passing	1.General Limits	-	100	100	100	90-100	45-70	15-40	8-27	4-16	2-6	6.0-8.0
	2.JMF Range	-	100	100	100	90-100	45-70	15-40	8-27	4-16	2-6	6.0-6.6
	3.Target Value	-	100.0	100.0	100	93	56	32	23	9	4	6.2

Asphalt Grade
<u>PG</u> 64-22

Recommended for Approval by Regional Director _____

Date: _____

Approved by Director, Materials Bureau _____

Date: _____

Remarks: _____